
A new life estimation method for lithium-ion batteries in plug-in hybrid electric vehicles applications

Simona Onori*

Center for Automotive Research,
The Ohio State University,
Columbus, OH, 43212, USA
E-mail: onori.1@osu.edu
*Corresponding author

Pierfrancesco Spagnol

Dipartimento di Elettronica e Informazione,
Politecnico di Milano Via Ponzio 34/5,
20133, Milano (MI), Italia
E-mail: spagnol@elet.polimi.it

Vincenzo Marano

Center for Automotive Research,
The Ohio State University,
Columbus, OH, 43212, USA
E-mail: marano.8@osu.edu

Yann Guezennec and Giorgio Rizzoni

Mechanical and Aerospace Engineering Department,
Center for Automotive Research,
The Ohio State University,
Columbus, OH, 43212, USA
E-mail: rizzoni.1@osu.edu
E-mail: guezenec.1@osu.edu

Abstract: This paper presents a new approach to life estimation for lithium-ion batteries used in plug-in hybrid electric vehicles (PHEVs) applications. A new framework for battery life estimation is developed which investigates the effects of two primary factors of battery life reduction in PHEVs applications, namely, depth of discharge (DOD) and temperature (T_{batt}), under typical driving conditions, driving habits, and average commute time of typical user over a year. This framework, whose development is built upon a weighted ampere-hour throughput model of the battery, is based on the novel concept of severity factor map which captures and quantifies the battery damage caused by different operating conditions. The proposed methodology can be a suitable tool to estimate battery life in terms of miles/year on-board of the vehicle.

Keywords: energy storage systems; plug-in hybrid electric vehicle; PHEV; battery lifetime estimation; battery ageing model.

Reference to this paper should be made as follows: Onori, S., Spagnol, P., Marano, V., Guezennec, Y. and Rizzoni, G. (2012) 'A new life estimation method for lithium-ion batteries in plug-in hybrid electric vehicles applications', *Int. J. Power Electronics*, Vol. 4, No. 3, pp.302–319.

Biographical notes: Simona Onori is a Research Scientist at the Ohio State University Center for Automotive Research (CAR). She joined CAR in October 2007 as a Postdoctoral Fellow. She received her Laurea degree Summa Cum Laude in Computer Science Engineering from University of Rome 'Tor Vergata' (Italy), her MS in Electrical Engineering from University of New Mexico (Albuquerque, NM, USA), and her PhD in Automation Engineering from University of Rome 'Tor Vergata' in 2003, 2004 and 2007, respectively. She is a SAE, IEEE and ASME member. She serves as an Associate Editor for the ASME. Her background is in control system theory. Her research focuses on energy management control and optimisation for HEV and PHEV, fault diagnosis and prognosis with application to automotive systems, ageing and characterisation of advanced batteries.

Pierfrancesco Spagnol¹ received his Master's degree in Automation Engineering from Politecnico di Milano in 2007 discussing a thesis on the design and development of algorithm strategies for drive-away in electric parking brake. He worked as a Research Assistant for Chassis Control System of FIAT Automobiles in 2008 and he was full-time Software Engineer for the advanced R&D mechatronic department of Brembo Spa. From July 2009 to May 2010, he was a Visiting Scholar at the Center for Automotive Research Ohio State University, working on aging and characterisation of advanced batteries.

Vincenzo Marano is a Senior Research Associate at The Ohio State University Center for Automotive Research (CAR). He started his collaboration with CAR in 2005 while working on his PhD and was appointed as a Postdoctoral Research Fellow in 2007. He received his Laurea degree in Mechanical Engineering in 2003 and his PhD in Mechanical Engineering in 2007, all from the University of Salerno, Italy. His research interests are in the areas of energy systems and alternative vehicles. He coordinates and conducts research on plug-in electric vehicles (PEVs), energy storage, energy management, control strategies for PEVs, their interaction with renewable energy sources and the grid, macroeconomics and energy policy.

Yann Guezennec is a Professor of Mechanical and Aerospace Engineering at The Ohio State University. He has a degree Cum Laude from the Institut National des Sciences Appliquées, France and a PhD in Mechanical and Aerospace Engineering from the Illinois Institute of Technology. His research interests lie in the field of advanced internal combustion engines, after-treatment systems, hybrid electric vehicles and fuel cell systems for automotive applications. He has developed significant research activities in the area of electro-thermal modelling of advanced batteries, battery ageing and diagnostics for HEV and PHEV applications.

Giorgio Rizzoni is the Ford Motor Company Chair in Electro Mechanical Systems at The Ohio State University, where he is a Professor of Mechanical and Electrical Engineering. He received his BS, MS and PhD in Electrical and Computer Engineering in 1980, 1982, and 1986, respectively, all from the University of Michigan. Since 1999, he has been the Director of the Ohio State University Center for Automotive Research (CAR). His research interests are in future ground vehicle propulsion systems, including advanced engines, electric and hybrid-electric drivetrains, advanced batteries, and fuel cell systems. He is an SAE Fellow (2005) and an IEEE Fellow (2004).

1 Introduction

PLUG-IN hybrid electric vehicles (PHEVs) are regarded today as one of the most promising technologies for transportation petroleum displacement and greenhouse gas emission reduction (Markel et al., 2008). The achievement of PHEV energy economy comes not only from the PHEV energy management control strategies implemented on-board of the vehicle, but also from PHEV design and extended energy storage (Tulpule et al., 2009). In this scenario, lithium-ion batteries are starting to play an important role in our mobility because of their advantages over other battery technologies and they are recognised as being best suited for fulfilling the requirements of this vehicle technology (Axen et al., 2008). Their high specific power and energy density content allow overcoming the limitations typical of Ni-MH batteries in meeting the power and energy demands of electric vehicles (EV) and hybrid electric vehicles (HEV) and, in addition, they withstand a wider range of temperatures.

The current battery price of Li-Ion batteries is one of the major disadvantages, though, which prevents PHEV market penetration, as the current cost of lithium-ion batteries is estimated to be about \$1,000/kWh, and the long term goal that would facilitate speedy introduction of PHEVs is \$250/kWh (Shiau et al., 2009). Economies of scale could definitely reduce the cost of the batteries per kWh, but still this rechargeable energy storage system remains the most expensive component of the vehicle.

Improvements are needed in order to make lithium-ion batteries more competitive, in particular, battery longevity, safety, reliability and lifetime prediction are key issues that need to be addressed fairly soon before assisting to a high market penetration of this technology, as they represent key barriers to commercialisation of PHEVs (Dubarry and Liaw, 2007; Pesaran et al., 2009; Wang et al., 2011).

The problem of understanding how to assess battery life degradation and battery performance during vehicle operation is of primary importance in this context. In particular, the focus of this paper is to address the question: “how can we suitable quantify battery degradation under real-world operating conditions?”

Knowing the battery useful life in automotive applications is crucial in order to guarantee performance and durability of the battery and limit the risks of premature failure. A successful battery lifetime prediction approach requires knowledge of the ageing processes, the factors which determine the ageing itself and their combined effects (Ruddell and Svoboda, n.d.).

Performance degradation affecting electrochemical energy storage systems is due to factors such as current severity (or C-rate), elevate temperature, discharge rate, *DOD*, amount and frequency of overcharge (Wang et al., 2011; Serrao et al., 2005). Moreover, battery ageing can be accelerated by factors from the driver such as combination of cycling, irregular patterns of charge and discharge cycles (Sauer and Wenzl, 2008). Thus, in approaching life estimation methods design, requirements of the driver (power and energy demand) together with other external factors like the temperature distribution within the battery, *DOD* and *SOC* of the battery need to be accounted for.

This paper focuses on developing a novel approach for battery life estimation in PHEV applications. The paper is organised as follows: in Section 2, methods for battery life estimation proposed in the open literature are reviewed. A framework for battery life prediction based on an accumulated ageing model (Serrao et al., 2009) is discussed in Section 3. Within this framework, a weighted Ah-throughput model for life estimation is presented with the new concept of severity factor map. Assessment analysis of the battery

life estimation method proposed is discussed in Section 4 for a PHEV case study. Finally, conclusions are given in Sections 5.

2 Review of battery life estimation methods

Two different approaches to battery lifetime estimation and prediction modelling are found in the open literature, namely: *performance-based models* and *weighted ampere-hour (Ah)-throughput models*. The performance-based models account for the rate of change of battery parameters while the various ageing processes take place. These models are potentially very accurate for making technical and financial decisions. The weighted Ah-throughput models, on the other hand, relate the end of life of a battery to some parameters which can be easily determined, such as Ah-throughput, number of cycles and time since manufacturing. Although these models are inherently limited in their accuracy, they are the only available as planning tools which incorporate battery lifetime features. These two classes of modelling approaches are briefly reviewed in this section.

2.1 Performance-based models

The battery lifetime and the battery end-of-life (EoL) can be expressed as function of different *performance parameters*. These parameters, such as the battery voltage, current, uptake power, *SOC*, etc., can be modelled through various parameterised models (Pesaran et al., 2007). These models, though, suffer in managing the changes in performance values of the battery due to ageing processes (Wenzl, et al., 2005). The performance is usually characterised using battery models, such as:

- electrochemical models
- equivalent circuit models
- analytical models with empirical data fitting
- artificial neural networks.

Electrochemical models provide detailed information on local conditions and performance (e.g., temperature, potential, current, electrolyte concentration etc.). On the other hand, they require specific knowledge of the chemical and physical interactions, e.g., porosity of the active materials, electrolyte volume and density, etc. Because of its intrinsic complexity the computational speed of the simulation is low (Smith et al., 2008).

In *equivalent circuit models* the battery is represented by components of an equivalent electric circuit like voltage and current sources, resistors and capacitors. The ageing process is represented by the change of the values of the equivalent circuit components. This type of models is very common for predicting battery dynamic characteristics (Liaw et al., 2005; Dubarry and Liaw, 2007). A first study of an ageing model for predicting battery life, able to capture the slow variation of model parameters with ageing (and with factors contributing to ageing such as C-rate, *DOD* and temperature) is presented in (Serrao et al., 2009).

In *analytical models*, with empirical data fitting, the lifetime is predicted by means of interpolation and extrapolation from test results and field data, which, in turn, require a lot of data (Rong and Pedram, 2003).

Artificial neural networks have a tremendous potential to discover relationships between inputs (operating conditions) and outputs (ageing processes and performance values). This approach to modelling does not rely on a detailed understanding of the mechanism which link input and output, but measurements are needed to derive the model (Yamazaki et al., 1998; Mukherjee, 2003).

2.2 Weighted Ah-throughput models

The second class of modelling framework for battery lifetime prediction uses models which relate the EoL of a battery to parameters such as Ah-throughput, number of cycles or time since manufacturing. Once a predetermined value of the parameter has been exceeded, the battery is considered to have reached its EoL. The overall Ah-throughput depends on the actual operating conditions. At the cell level, the severity of the charge transfer depends on the current severity relative to the battery size² (C-rate), the battery temperature T_{batt} and the *DOD*. The weighted Ah-throughput models are based on the assumption that under particular standard conditions (e.g., given C-rate, T_{batt} and *DOD*) a battery can only achieve a given Ah-throughput until the EoL is reached. For automotive applications a battery is considered reaching its EoL when it shows a capacity loss of 20% or more with respect to the original capacity (Wenzl et al., 2005).

These models account for the fact that deviations from the standard operating conditions (in terms of C-rate, T_{batt} , *DOD*) may increase or decrease the physical Ah-throughput a battery can give and consequently the rate of ageing. A measure of the effective Ah-throughput is given by:

$$Ah_{eff} = \sum w_E \cdot n_E \cdot Ah_E \quad (1)$$

where

Ah_{eff} weighed Ah-throughput, i.e., effective Ah-throughput that the battery can achieve before reaching its EoL.

E an event is characterised by a particular instance of current load of fixed magnitude under a given temperature, *DOD* and initial *SOC*. It is generated from the discretisation or segmentation of the current signal. The duration of an event, i.e., the step of discretisation, is decided in the implementation phase and can be either fixed or time varying.

w_E weigh or severity associated with an event E .

n_E number of events E .

Ah_E Ah-throughput over an event E .

The battery is considered to fail and reach its EOL when the effective Ah-throughput, as obtained from the model of equation (1), is greater than the total Ah-throughput measured under nominal operating conditions (e.g., discharge/charge at fixed current rate and fixed *DOD*) as provided by the battery manufacturer.

If, from one hand, this type of models represent a good option for the lifetime estimation of batteries in PHEVs because of their easy structure which allows for very high computational speed and adaptation to different battery technologies, on the other hand, the determination of the parameters for the weighting factors remain an issue. In this paper we refer to the weighting factors as severity factors, which are responsible for reduced lifetime. Accurate values of these factors would require extensive data collection, not yet available.

The approach to life estimation presented in this paper is based on the weighted Ah-throughput models. Generally, battery nominal life (20% loss in capacity) is measured by the manufacturers under 100% *DOD* cycles. Cycles with lower *DOD* have minor effects on performance degradation (in terms of loss in capacity, increase in resistance), thus resulting in a typical ‘throughput’ type model, where the total number of partial and full cycles are proportionally added together to find out how much of the life has been expended (a curve of expected cycle number vs. *DOD* of each cycle is found in (Chan et al., 2001).

Battery life depends on the interaction of operating conditions or severity factors and ageing characteristics and it is, indeed, a highly non-linear process.

At the pack (vehicle) level, the determining factor for pack ageing and life is going to be the most aged cell, strongly impacted by both electrical cell balancing/BMS and thermal design/management. Our focus here is on cell level and generalisation to the vehicle level under assumption of all cells equivalent.

Battery requirements differ according to the specific application. High power is needed to provide adequate boost in HEV applications, while power density is less important in PHEV and EV applications due to their larger battery pack. On the other hand, as energy translates into vehicle range, high energy is needed to provide adequate mile range. This is more important for PHEVs and EVs rather than for HEVs. In fact, a HEV battery is operated in charge sustaining mode at intermediate SOC through shallow cycles and only uses a small portion of the available energy. Thus, HEV batteries differ from PHEV and EV batteries, in that they require higher power density than energy density. In this paper, in virtue of the application under consideration, the capacity is considered as the only ageing parameter that effects battery life and thus, life characteristics of the battery are defined based on its residual capacity.

3 A severity factor map-based framework for battery lifetime estimation

Prediction of battery life is achieved through an ageing model which expresses the ageing of the battery in terms of variation of damage variables, i.e., the physical or functional parameters of the battery whose value changes irreversibly because of ageing and modify the behaviour of the system. The approach to ageing modelling presented in Serrao et al. (2009) is briefly reviewed in this section. A generic dynamic system subject to ageing can be described by the following set of dynamics equations:

$$\begin{aligned}\dot{x} &= f(x, \mathcal{G}, u) \\ \dot{\mathcal{G}} &= \varepsilon \cdot g(\mathcal{G}, p) \\ y &= C \cdot x + D \cdot u + v\end{aligned}\tag{2}$$

where

- x state variables associated to the fast dynamics
- \mathcal{G} damage variables associated with slow dynamics
- u external inputs
- p vector of internal/external ageing factors (including x and u)
- y is the set of system outputs, dependent on the constant matrices C and D and on the measurement error v
- ε positive scalar ($\ll 1$) representing the fact that the dynamics of the damage variables are much slower than the system dynamics

Variation of damage variables (\mathcal{G}) implies slow changes in the system behaviour, hence ageing.

To express the progression of the ageing process the normalised damage measure ξ is introduced as:

$$\xi(\mathcal{G}) = \frac{\mathcal{G}_0 - \mathcal{G}}{\mathcal{G}_0 - \mathcal{G}_f} = \frac{S_0 - S}{S_0 - S_f} \quad (3)$$

The damage measure ξ is a scalar index varying between 0 and 1. A value of $\xi = 0$ indicates a new battery ($\mathcal{G} = \mathcal{G}_0 =$ known initial value of the ageing parameter) while $\xi = 1$ indicates a ‘dead’ battery ($\mathcal{G} = \mathcal{G}_f =$ predefined value of the ageing parameter corresponding to battery EoL). Since we are assuming that the capacity is the only ageing parameter, equation (3) is also expressed in terms of the initial (S_0) and final value (S_f) of the capacity S corresponding to a new and EoL battery, respectively. Rewriting the ageing equation $\dot{\mathcal{G}} = \varepsilon \cdot g(\mathcal{G}, p)$ in equation (2) in terms of ξ and the number of cycles n , rather than \mathcal{G} and time, (with a simple rescaling of the variables) leads to the equation:

$$\frac{d\xi}{dn} = \varphi(\xi, p) \quad (4)$$

The progression of ageing, i.e., the slope of the curve ξ as given by equation (4), depends on the value of the ageing factors p and the present age ξ .

Equation (4) can be used to predict the evolution of battery damage.

In Serrao et al. (2009), it is shown that, if the capacity evolution is to be predicted, then the progression of ageing, described by the non-linear coupled equation (4) can be expressed as:

$$\frac{d\xi}{dn} = \varphi(\xi, p) = \varphi_1(\xi) \sigma(p) \quad (5)$$

Equation (5) expresses the progression of ageing as a decoupled function of the actual ageing and the actual operating conditions and allows for tracking the progression of ageing if the functions $\varphi_1(\xi)$ and $\sigma(p)$ are known. These two functions are defined as ‘ageing factor function’ and ‘severity factor function’, respectively. The ageing factor

function is a quantitative measure of the past ageing occurred at the battery at a given moment of its life, while the severity factor function expresses and quantifies the amount of damage due to the operating conditions (or severity factors) such as: T_{batt} , DOD , current directionality, C-rate, driving patterns, etc.

In this work, focus is given on the characterisation of the severity factor function $\sigma(p)$ and its use for estimating battery life for PHEV applications. By knowing the map $\sigma(p)$ under different operating conditions, a quantitative assessment of battery performance can be performed and used in the weighted Ah-throughput model previously described by equation (1) for life estimation.

Ongoing research is devoted to develop models to incorporate the life estimation method presented in the paper (in the form of severity factor map) within a prognostics framework. The validation of the severity factor map, as well as the verification of the ageing model framework requires an extensive campaign of experiments which are ongoing at the Center for Automotive Research The Ohio State University (CAR-OSU).

3.1 Severity factor map characterisation for PHEV applications

As mentioned in the Introduction, at the cell level, among the ageing factors that affect the battery life in PHEV applications (Freedom Car Manual, 2008) the two most important considered in this study are:

- battery temperature, T_{batt}
- DOD

Notice that, while in HEV applications current C-rate ranges within $\pm 15C$, which contribute to significant severity and therefore ageing, the C-rate effect on battery ageing can be neglected in PHEV applications. In fact, being the battery oversized in PHEVs, typical current C-rates range between $\pm 4C$. An example of current profile corresponding to a charge-depleting PHEV on a US06 driving cycle is shown in Figure 1, and the statistical distribution of the C-rate is shown in Figure 2.

Figure 1 Typical current (c-rate) profile for a PHEV (in charge-depleting mode) during an us06 driving cycle

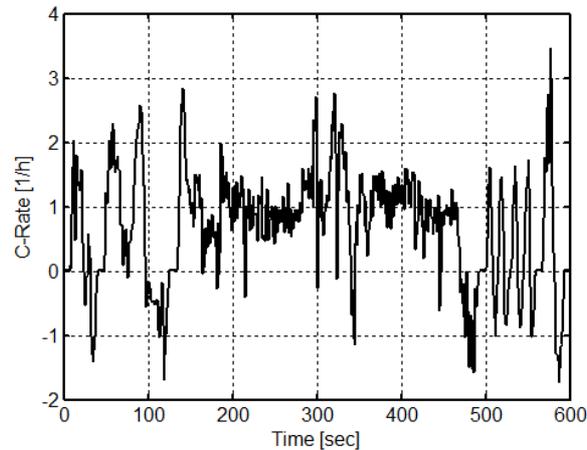
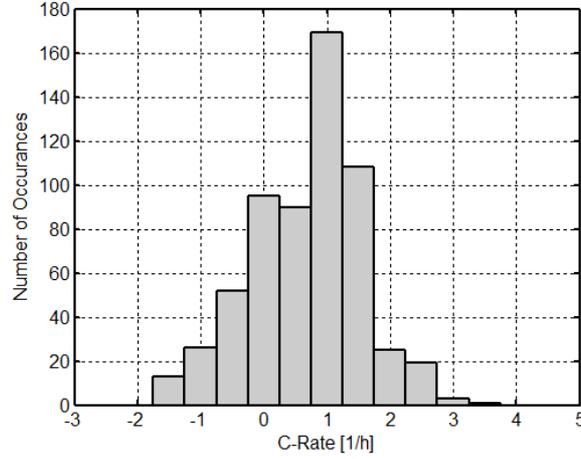


Figure 2 Current (C-rate) statistical distribution for a PHEV (in charge-depleting mode) during an us06 driving cycle

This observation implies that the vector $[T_{batt}, DOD]$ represents the vector p of ageing factors used in the damage accumulation model of equation (6).

Usually, battery manufacturers define battery life with respect to a nominal cycle $(I_n(t))$ with these characteristics: C-rate = 1, $DOD = 100\%$, $T_{batt} = 25^\circ\text{C}$. Thus, battery life is defined as the overall Ah-throughput (in and out charge from 0 to EoL) when the battery is subject to cycle $I_n(t)$:

$$Ah\text{-throughput}_{nominal} = \int_0^{EoL} |I_n(t)| dt \quad (6)$$

The ageing effects caused to the battery by any other cycle are quantified by the relative severity factor σ when given with respect to the nominal cycle or 'baseline'. In particular, the severity factor σ at a given $DOD = \overline{DOD}$ and $T_{batt} = \overline{T_{batt}}$ is defined as:

$$\sigma(\overline{DOD}, \overline{T_{batt}}) = \frac{Ah\text{-throughput}_{nominal}}{\int_0^{EoL} |I(t)| dt} \quad (7)$$

where the quantity $\int_0^{EoL} |I(t)| dt$ indicates the overall Ah-throughput corresponding to cycle the battery at current $I(t)$ under conditions $DOD = \overline{DOD}$ and $T_{batt} = \overline{T_{batt}}$. The severity factor represents the relative ageing effect with respect to the baseline given by the nominal cycle. A severity factor σ greater than 1 represents conditions which are more severe than the baseline in terms of ageing.

The determination of the relative severity factors to form the overall severity factor map (namely, the function $\sigma(p)$ in equation (5) on the domain of interest (i.e., DOD and T_{batt}) is typically difficult to obtain and is very dependent on the particular battery chemistry, anode and cathode composition and construction. Furthermore, all information related to ageing characteristics even for a given cell, requires extensive and very lengthy

(hence costly) data collection. For the purpose of this paper, a prototypical example of ageing severity factor map was extracted from battery manufacturer data, albeit with considerable difficulty as the tests were not necessarily conducted with our framework in mind. For the purpose of illustration of the methodology, an estimate of the value of severity factor as a function of operating temperature and DOD is given based on publically available data (Markel and Simpson, 2006; A123, 2007). This severity factor surface will be referred to as ‘estimated’ in the remainder of this paper. The topology of this ‘estimated’ severity factor map, while specific to a particular cell and very lengthy to determine experimentally, is generic enough in its overall shape. On a real vehicle application, though, the actual ageing conditions (wide range of temperature and low state of charge) are different from the ones considered to obtain those data. Hence, the need to carry out a campaign of ageing experiments meant to collect data reflecting actual operations of the battery on the vehicle is unquestionable.

The ‘estimated’ or postulated severity factor map, $\sigma_{T_{batt}, DOD}$ as a function of T_{batt} and DOD , is shown in Figure 3. In the rest of the paper, the symbol $\sigma_{T_{batt}, DOD}$ indicates the overall severity factor map (Figure 3) while $\sigma(\overline{DOD}, \overline{T_{batt}})$ indicates the severity factor value as obtained when the battery is cycled at $DOD = \overline{DOD}$ and $T_{batt} = \overline{T_{batt}}$.

Two regions on the severity factor map are of main interest: a *fringe spot* and a *sweet spot*. If the battery is operating in a *fringe spot* the Ah-throughput will be weighted with a severity factor higher than the severity factor used when the battery is operating in the sweet spot, which, in turn, reflects the more severe operating conditions. In fact, working at high temperature ($> 25^{\circ}\text{C}$) and wide DOD will result in an accelerated ageing of the battery. The severity factor as a function of the DOD , parameterised in temperature, is shown in Figure 4.

Figure 3 Severity factor map for PHEV applications

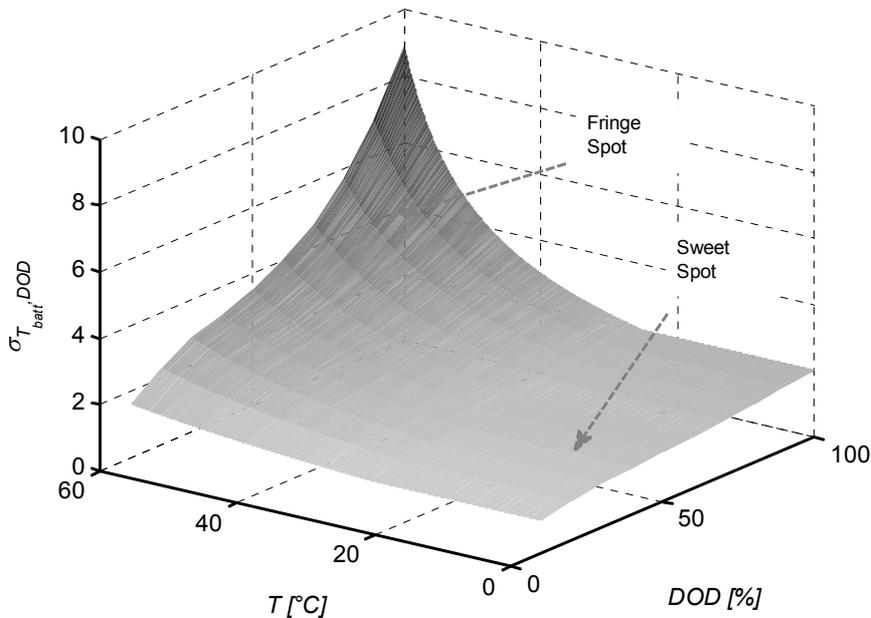
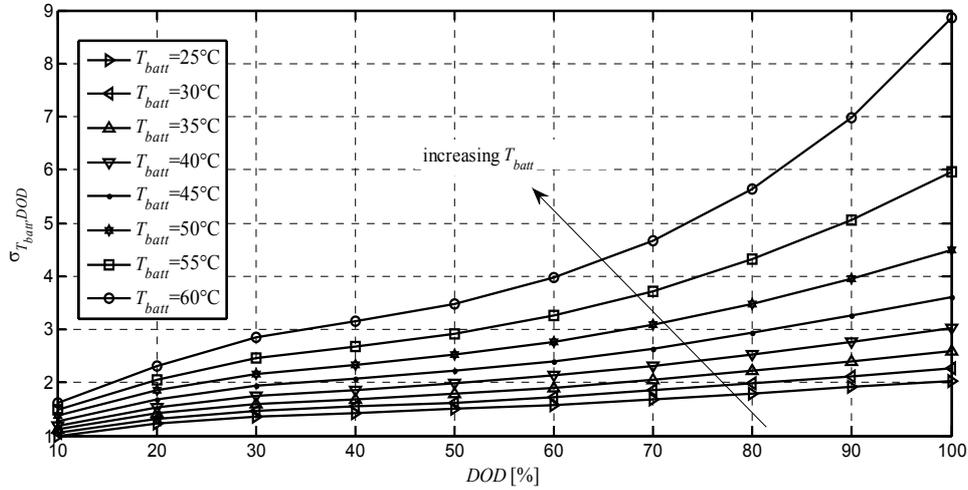


Figure 4 Severity factor as function of *DOD* parameterised with respect to battery temperature

A targeted design of experiments is being conducted to validate the shape of the severity factor map over the battery operating domain. Not only will the verification of the severity factor map through experiments be a valid tool to assess battery life but also it can be used as a guideline to better design PHEV control strategies. In fact, it can be used to investigate the possibility of making the charge sustaining operation happen at lower *SOC* than the one effectively used in vehicle now (typically 30% *SOC*) by looking at what degradation level the battery will be reaching. In general, important insights can be derived from the qualitative behaviour of the severity factor map for more conscious control strategies concerning fuel consumption minimisation as well as battery life extension.

4 Case study: preliminary simulation results

In this section, simulation results coming from exploiting the severity factor map to estimate battery longevity using an energy-based model of a hybrid powertrain are presented.

The simulator used in this study, is built upon the energy-based model of Cx-Sim (Tulpule et al., 2010), and adapted to PHEV applications. Table 1 describes the main vehicle characteristics. The vehicle is based on a series-parallel architecture, which includes a diesel engine coupled to a belted starter alternator (BSA) on the front axle and an electric motor (EM) on the rear axle. This configuration allows for a variety of modes such as pure electric drive, electric launch, engine load shifting, motor torque assist, and regenerative braking.

The considered vehicle requires approximately 370 Wh/mile for electric mode in UDDS cycle, thus resulting in about 11 kWh of stored energy required to run 30 miles in AER. To account for battery ageing and performance issues, the usable *SOC* has been assumed in the range 0.25–0.95; starting from this assumption the total storage capacity of the battery needs to be about 16 kWh.

Table 1 Basic vehicle modelling parameters

Class	SUV
Mass	2130 kg
Engine	1.9L Diesel
Battery pack	16 kWh (50 Ah × 312V)
Control strategy	Charge depleting-charge sustaining mode

The implemented control strategy is based on charge depleting-charge sustaining energy management policy. In charge depleting mode (or pure electric), the battery is used to drive the vehicle until the electric machine is able to supply required power and the battery *SOC* is greater than the designed lower limit. Once *SOC* reduces below the minimum allowable value (0.3), the vehicle is operated in charge sustaining mode for the remaining of the trip, where an equivalent consumption minimization strategy (ECMS) is implemented (Serrao et al., 2011; Tulpule et al., 2010).

Table 2 Driving and charging events

<i>Driving/charging events</i>	
T1	UDDS+US06 (trip to work after full charge). Initial SOC is 0.95
T1b	US06+UDDS (trip to home after work). Initial SOC is the final SOC of previous trip
T1c	US06+UDDS (trip to home after work). Initial SOC is 0.95
T2	UDDS (errands). Initial SOC is the final SOC of previous trip
T2b	UDDS (errands). Initial SOC is 0.95
T3	UDDS+HWFET+HWFET+HWFET+HWFET+UDDS (this assumes the vehicle is only recharged at the end of the day). Initial SOC is 0.95
C	Charging from SOC 0.25 to 0.95. Charging capability: 6 kW (AC: 220V, 30A; DC: 20A CC/CV)

In order to simulate statistically meaningful scenarios, driving and charging events characteristic of a typical user were used (Table 2) (Sikes et al., 2010) and then combined in a way to compose typical days of driving to reflect common driving habits, and average commute time over a year (Table 3).

Table 3 Typical days


<i>Days</i>	<i>Combination of events</i>	<i>Frequency</i>
D1a	T1-T1b-T2-C	3 days/week, 48 weeks/year (tot. 144 days/year)
D1b	T1-C-T1c-C-T2b-C	Alternative to D1a
D2a	T1-T1b-C	2 days/week, 48 weeks/year (tot. 96 days/year)
D2b	T1-C-T1c-C	Alternative to D2a
D3	T3-C	2 days/week, 48 weeks/year + 7 days/week, 4 weeks/year (tot. 124 days/year)

Different charging availability is also considered. Two main scenarios have been inspected: controlled charging (once a day, overnight) and uncontrolled charging (charging is possible whenever the vehicle is parked).

Simulation results show that through an uncontrolled charging a better fuel economy can be achieved, but at the price of reduced battery life. Other issues are related to the possible overload of the power grid, but this will not be discussed in this paper.

The combination of the described events and typical days results in approximately 15,000 miles/year.

Figure 5 Speed profile of typical day D1a

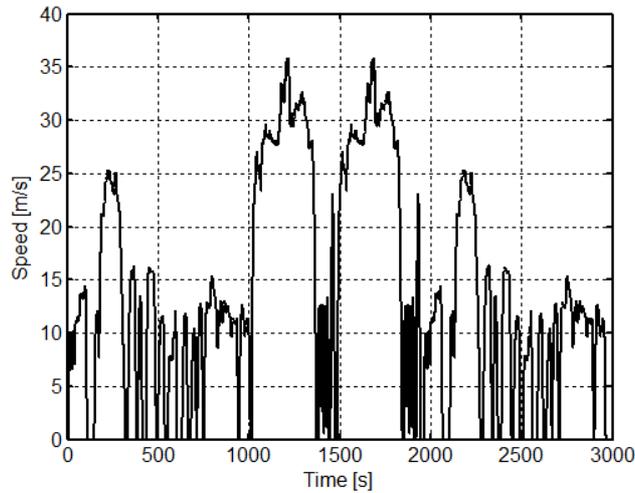

Note: This profile is the same as D1b (they only differ from the initial soc the battery is discharged from and the charging event).

4.1 Weighted Ah-throughput calculation


The approach used to estimate battery life is structured according to the schematic of Figure 6. The battery model used in this study takes the battery current, I_{batt} , over a driving mission and the ambient temperature, T_{amb} , as inputs and gives the battery voltage, V_{batt} and the battery temperature T_{batt} as outputs (Muratori et al., 2011). Then, $\overline{T_{batt}}$ and the \overline{DOD} (derived from the battery model and I_{batt}) are given as inputs to the severity factor map which, once interrogated, returns the value of severity occurring to the battery under those particular conditions. The severity factor value is then used in the accumulated Ah-throughput model through the equation:

$$Ah_{eff} = \int_0^T \sigma(\overline{DOD}, \overline{T_{batt}}) |I_{batt}(t)| dt \quad (8)$$

This gives the weighted Ah-throughput or accumulated weighted Ah that the battery has effectively experienced over a trip of length T . From an implementation point of view, the value of the severity factor can be extracted from the map either at each sampling time or over a more meaningful simulation window of seconds or minutes. In

this latter case, average values should be used. In this simulation study, a fixed window of two minutes was used to extract the information needed to interrogate the severity factor map.

Figure 6 Schematic of model-based structure for battery life estimation

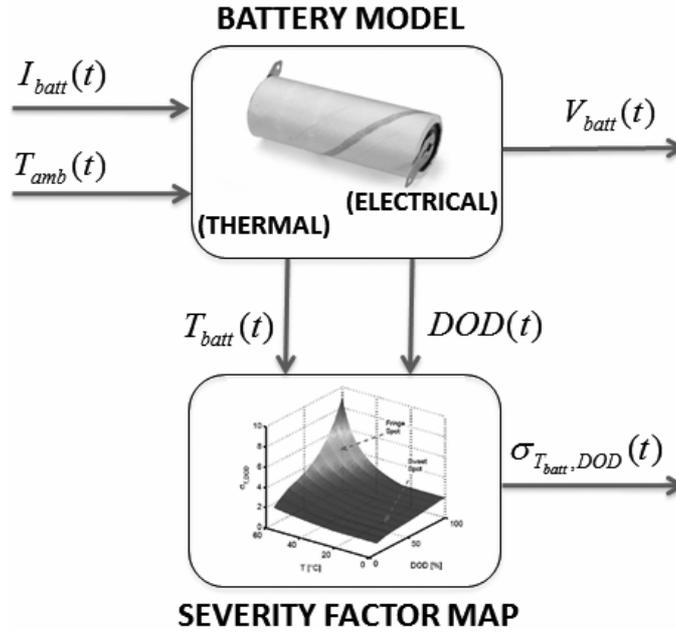

The battery Ah-throughput or accumulated Ah, given as $Ah = \int_0^T |I_{batt}(t)| dt$, is also outputted by the model.

Preliminary simulation results were obtained using the overall battery model (Figure 6) and data (electric power, and battery current) from the PHEV simulator presented earlier under statistically representative common driving/charging scenarios. Table 4 shows the two outputs of the model (Ah-throughput and weighted Ah-throughput) for the series of driving/charging events of Table 2. The average C-rate and the total miles travelled over each events are also given in Table 4.

It is worth observing that the C-rate results in a very shallow severity characteristic over all the events, which subsides the assumption to neglect it as primary ageing factor in this study. The same comparison is then performed over typical days and shown in Table 5.

Table 4 Comparison between Ah and weighted Ah on different driving events

	T1	T1b	T1c	T2	T2b	T3	C
Ah	33.98	6.65	33.98	2.47	9.6	50.62	35.0
Weighted Ah	43.99	10.51	44.55	4.47	9.82	72.11	39.05
Average C-rate [A/Ah]	1.66	0.32	1.66	0.23	0.8	0.68	0.4
Total miles	15.45	15.45	15.45	8.0	8.0	57.0	-

Table 5 Comparison between Ah and weighted Ah on typical days

	<i>D1a</i>	<i>D1b</i>	<i>D2a</i>	<i>D2b</i>	<i>D3</i>
Ah	78.1	182.56	75.63	110.63	85.62
Weighted Ah	98.02	215.51	93.55	166.64	111.16
Total miles	38.9	38.9	30.9	30.9	57.0

Figure 7 SOC profile (dot-dot) and comparison between Ah-throughput (solid) and weighted Ah-throughput (dashed-dot) for the day D1a (see online version for colours)


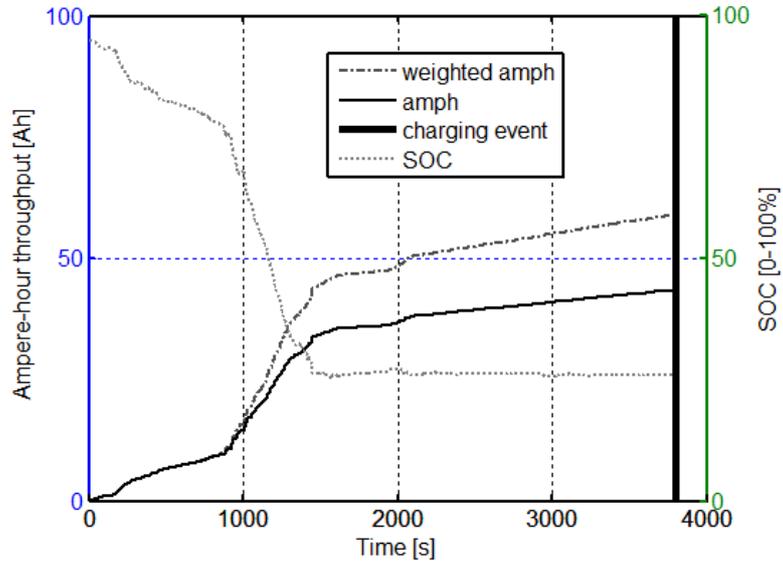


Figure 8 SOC profile (dot-dot) and comparison between Ah-throughput (solid) and weighted Ah-throughput (dashed-dot) for a typical day D1b (see online version for colours)

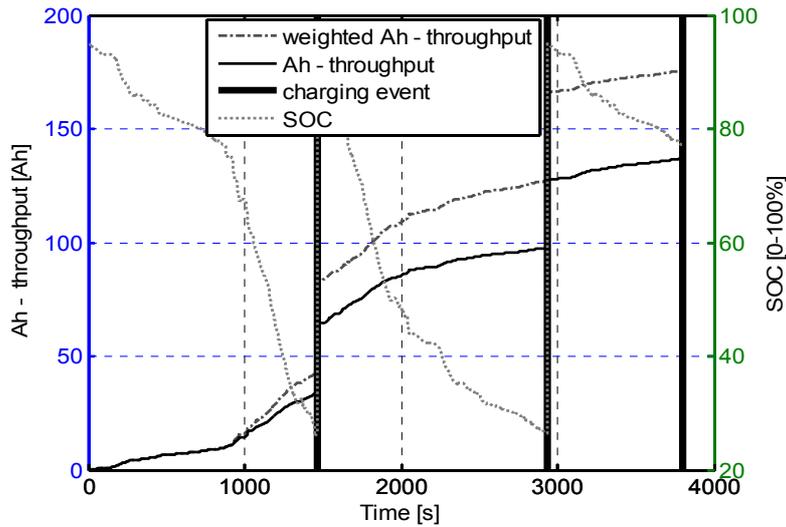

Results showing the difference between accumulated Ah and accumulated weighted Ah are in Figure 7 and Figure 8. In Figure 7 it is shown a charge depleting-charge sustaining behaviour, which results in a battery *DOD* of 0.65 for more than half of the cycle, while in the case shown in Figure 8 the vehicle never operates in charge sustaining due to the repeated charges.

Results show that there are significant differences between accumulated Ah and accumulated weighted Ah as a result of accounting for the cycle severity through the severity factor map, which considerably adjust the life battery expectation as a function of different usage patterns.

Table 6 Expected life example

	<i>Uncontrolled charging (charge at home/work)</i>	<i>Controlled charging (charge only at home)</i>
Ah	47,526	29,124
Weighted Ah	60,814	36,879
Total miles		15,636
Total miles in electric	12,243	6,458
% miles in pure electric mode	78.3	41.3
Nominal capacity (Ah)		50
Expected cycle life at 100% <i>DOD</i> $\pm 1C$		2,500
Estimated life (years)	8.34	13.76

The expected cycle life and estimated battery life are also assessed under two different charging scenarios as reported in Table 6. This case shows how different charging strategies (either controlled or uncontrolled), which would result in different *DOD* experienced in pure electric mode (the ability to charge the battery more frequently ensure lower excursion in the *SOC*) leads to considerably different expectation of battery life.

5 Conclusions

This paper has presented a novel framework to estimate life of Li-ion batteries in PHEV applications. The new concept of severity factor map has been introduced which is used to quantify the damage occurring to the battery under different driving scenarios, charging availability and usage patterns. Starting from data provided by battery manufacturer, the severity factor map has been designed and quantitatively postulated. This tool, framed within a battery model, is used to give an estimate of battery life in terms of effective Ah-throughput experienced by the battery when used in every day driving scenarios. Preliminary simulation results have shown that different battery usages, corresponding to different driving scenarios and charging events, have a different impact on battery life. Uncontrolled and widely available charging infrastructure would lead to better fuel economy (more miles in EV mode), but at the price of a strongly reduced life (results show a reduction of about 40% in terms of calendar life). The approach described in this paper is fairly generic and has the potential to be applicable to any classes of vehicles, with a fairly simple battery model, as long as the ambient temperature and the battery current are measured on-board of the vehicle. Ageing

experiments are currently underway to calibrate the severity factor map, through cycles representative of real driving characteristics.

References

- A123 (2007) *High Power Lithium Ion ANR26650M1A – Datasheet Specs*, available at http://www.a123systems.com/cms/product/pdf/1/_ANR26650M1A.pdf (accessed in 2008).
- Axen, J., Burke, A. and Kurani, K. (2008) *Batteries for Plug-In Hybrid Electric Vehicles (PHEVs): Goals and the State of Technology*, University of California: Institute of Transportation, Davis, CA.
- Chan, T., Li, Z. and Ko, J. (2001) 'Fatigue analysis and life prediction of bridges with structural health monitoring data – Part II: application', *International Journal of Fatigue*, Vol. 23, No. 1, pp.55–64.
- Dubarry, M. and Liaw, B. (2007) 'Development of a universal modeling tool for rechargeable lithium batteries', *Journal of Power Sources*, Vol. 174, No. 2, pp.856–860.
- Freedom Car Manual (2008) *Battery Test Manual For Plug-In Hybrid Electric Vehicles*, U.S. Department of Energy Vehicle Technology Program.
- Liaw, B., Jungst, R., Nagasubramanian, G. and Case, H. (2005) 'Modeling capacity fade in lithium-ion cells', *Journal of Power Sources*, Vol. 140, No. 1, pp.157–161.
- Markel, T. and Simpson, A. (2006) 'Plug in electric vehicle energy storage system design', *Advanced Automotive Battery Conference*, Baltimore, Maryland.
- Markel, T., Smith, K. and Pesaran, A. (2008) 'PHEV energy storage performance/life/cost tradeoff analysis', *8th Advanced Automotive Battery Conference*, Tampa, FL.
- Mukherjee, A. (2003) *Advances in Battery Management Using Neural Networks and Fuzzy Logic*, I.N. Cornell University (Ed.), School of Electrical and Computer Engineering.
- Muratori, M., Canova, M. and Guezennec, Y. (2011) 'A spatially-reduced dynamic model for the thermal characterization of li-ion battery cells', *International Journal of Vehicle Design*, Vol. 58.
- Pesaran, A., Markel, T., Tataria, H. and Howell, D. (2007) 'Battery requirements for plug-in hybrid electric vehicles – analysis and rationale', *Proc. of International Electric Vehicle Symposium*.
- Pesaran, A., Smith, K. and Markel, T. (2009) 'Impact of the 3Cs of batteries on PHEV value proposition: cost, calendar life, and cycle life', *Proc. of Advanced Automotive Battery Conference*.
- Rong, P. and Pedram, M. (2003) 'An analytical model for predicting the remaining battery capacity of lithium-ion batteries', *Proc. Design, Automation and Test in Europe Conf. and Exhibition*, pp.1148–1149.
- Ruddell, A. and Svoboda, V. (n.d.) 'Life prediction of batteries for selecting the technically most suitable and cost effective battery', *Journal of Power Sources*, Vol. 144, No. 2, pp.373–384.
- Sauer, D. and Wenzl, H. (2008) 'Comparison of different approaches for lifetime prediction of electrochemical systems – using lead acid batteries as example', *Journal of Power Sources*, Vol. 176, No. 2, pp.534–546.
- Serrao, L., Chebab, Z., Guezennec, Y. and Rizzoni, G. (2005) 'An aging model of Ni-MH batteries for hybrid electric vehicles', *Proceeding IEEE Vehicle Power and Propulsion Conference*.
- Serrao, L., Onori, S. and Rizzoni, G. (2011) 'A comparative analysis of energy management strategies for hybrid electric vehicles', *ASME Journal of Dynamic Systems, Measurement and Control*.
- Serrao, L., Onori, S., Rizzoni, G. and Guezennec, Y. (2009) 'A novel model-based algorithm for battery prognosis', *7th IFAC SAFEPROCESS*, Barcelona.

- Shiau, C.N., Samaras, C., Hauffe, R. and Michalek, J. (2009) 'Impact of battery weight and charging patterns on the economic and environmental benefits of plug-in hybrid vehicles', *Energy Policy*, Vol. 37, No. 7, pp.2653–2663.
- Sikes, K., Hadley, S., McGill, R., Cleary, T., Marano, V., Ungar, E. and Gross, T. (2010) *Plug-in Hybrid Electric Vehicle Value Proposition Study – Final Report*, Oak Ridge National Laboratory, Oak Ridge, Tennessee, Report Number ORNL/TM-2010/46 under DOE Contract DE-AC05-00OR22725.
- Smith, K., Rahn, C. and Wang, C. (2008) 'Model-based electrochemical estimation and constraint management for pulse operation of lithium ion batteries', *IEEE Transactions on Control Systems Technology*, May, Vol. 18, No. 3.
- Tulpule, P., Marano, V. and Rizzoni, G. (2009) 'Effect of different PHEV control strategies on vehicle performance', *American Control Conference*, St. Louis, MO, US.
- Tulpule, P., Marano, V. and Rizzoni, G. (2010) 'Energy management for plug-in hybrid electricvehicles using equivalent consumption minimisation strategy', *International Journal of Electric and Hybrid Vehicles (IJEHV)*, Vol. 2, No. 4, pp.329–350.
- Wang, J., Liu, P., Hicks-Garner, J., Sherman, E., Soukiazian, S. and Verbrugge, M. et al. (2011) 'Cycle-life model for graphite-LiFePO₄ cell', *Journal of Power Sources*, Vol. 196, No. 8, pp.3942–3948.
- Wenzl, H., Baring-Gould, I., Kaiser, R., Liaw, B., Lundsager, P. and Manwell, J. et al. (2005) 'Life prediction of batteries for selecting the technically most suitable and cost effective battery', *Journal of Power Sources*, Vol. 144, No. 2, pp.373–384.
- Yamazaki, T., Sakurai, K. and Muramoto, K. (1998) 'Estimation of the residual capacity of sealed lead-acid batteries by neural network', *Telecommunications Energy Conference*, San Francisco, CA, USA.

Notes

- 1 Piefrancesco Spagnol has conducted this work while he was a Visiting Scholar at Center for Automotive Research at The Ohio State University.
- 2 The C-rate is a measure defined as the ratio of the current (in A) to the nominal charge capacity (in Ah): $C\text{-rate} = I/S$ where S is the battery capacity.